

Van der Waals Engineering of Ultrafast Carrier Dynamics in Magnetic Heterostructures

Paulina Ewa Majchrzak, Yuntian Liu, Klara Volckaert, Deepnarayan Biswas, Chakradhar Sahoo, Denny Puntel, Wibke Bronsch, Manuel Tuniz, Federico Cilento, Xing-Chen Pan, Qihang Liu, Yong P. Chen, and Søren Ulstrup*



Cite This: *Nano Lett.* 2023, 23, 414–421



Read Online

ACCESS |



Metrics & More




Article Recommendations



Supporting Information

ABSTRACT: Heterostructures composed of the intrinsic magnetic topological insulator MnBi_2Te_4 and its nonmagnetic counterpart Bi_2Te_3 host distinct surface electronic band structures depending on the stacking order and exposed termination. Here, we probe the ultrafast dynamical response of MnBi_2Te_4 and MnBi_4Te_7 following near-infrared optical excitation using time- and angle-resolved photoemission spectroscopy and disentangle surface from bulk dynamics based on density functional theory slab calculations of the surface-projected electronic structure. We gain access to the out-of-equilibrium charge carrier populations of both MnBi_2Te_4 and Bi_2Te_3 surface terminations of MnBi_4Te_7 , revealing an instantaneous occupation of states associated with the Bi_2Te_3 surface layer followed by carrier extraction into the adjacent MnBi_2Te_4 layers with a laser fluence-tunable delay of up to 350 fs. The ensuing thermal relaxation processes are driven by phonon scattering with significantly slower relaxation times in the magnetic MnBi_2Te_4 septuple layers. The observed competition between interlayer charge transfer and intralayer phonon scattering demonstrates a method to control ultrafast charge transfer processes in MnBi_2Te_4 -based van der Waals compounds.

KEYWORDS: magnetic topological insulators, MnBi_2Te_4 , van der Waals heterostructures, ultrafast carrier dynamics, time- and angle-resolved photoemission spectroscopy, density functional theory

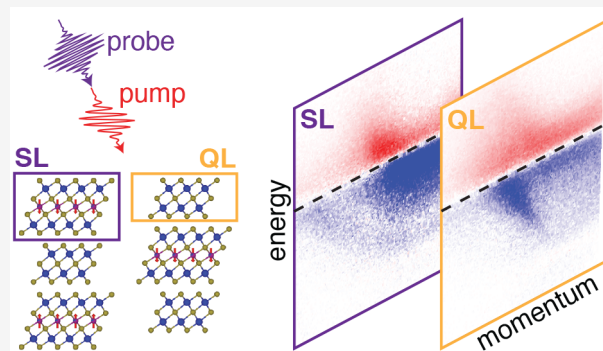


Heterojunctions composed of two-dimensional (2D) semiconducting materials are highly promising for developing novel optoelectronic devices due to tunable band gaps and charge carrier dynamics.¹ The interplay of charge and phonon interactions has been intensively examined in transition metal dichalcogenide heterostructures, unveiling a sub-50 fs interlayer carrier extraction that is ideal for light harvesting and photovoltaics.^{2,3} van der Waals compounds based on the antiferromagnetic topological insulator MnBi_2Te_4 present another attractive candidate for advanced opto- and spintronics applications due to the realization of exotic phases such as the quantum anomalous Hall effect and axion electrodynamics.^{4–12} Yet, optically induced ultrafast carrier dynamics and charge transfer processes in these materials remain largely unexplored. Moreover, the properties of these materials can be elegantly engineered via van der Waals stacking. For example, combining a quintuple layer (QL) of the nonmagnetic topological insulator Bi_2Te_3 with a septuple layer (SL) of MnBi_2Te_4 reduces the antiferromagnetic exchange interaction between neighboring planes of Mn atoms, while strengthening the affinity of the system to undergo a spin-flop transition to ferromagnetic order.¹³ As a

result, van der Waals heterostructures of the form $\text{MnBi}_2\text{Te}_4(\text{Bi}_2\text{Te}_3)_m$ ($m = 1, 2, 3, \dots$) offer a platform for exploring the interplay between the magnetic properties and the topological phases of matter.^{14–21} In order to gain access to the energy- and momentum-resolved ultrafast carrier dynamics of $\text{MnBi}_2\text{Te}_4(\text{Bi}_2\text{Te}_3)_m$ heterostructures, we employed time- and angle-resolved photoemission spectroscopy (TR-ARPES). This approach utilizes a near-infrared optical excitation to induce direct optical transitions from the occupied to the unoccupied states. The out-of-equilibrium charge carrier populations in the excited states are then measured by a time-delayed ultraviolet probe pulse, giving direct insights into charge transfer processes and phonon relaxation between bulk and surface states on a given

Received: August 3, 2022

Revised: January 4, 2023

Published: January 6, 2023



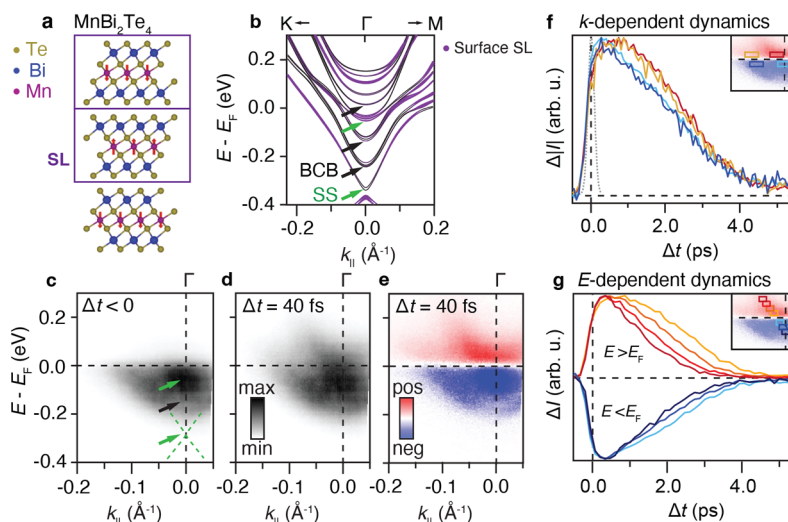


Figure 1. Surface electronic structure and excited state populations in MnBi_2Te_4 . (a) Overview of septuple layer (SL) crystal structure with spins on Mn atoms indicated by red arrows. (b) DFT slab calculation of surface-projected band structure shown as black curves with the weight of the projected bands indicated by purple circles. (c–e) Photoemission intensity (c) before the arrival of the pump pulse ($\Delta t < 0$) and (d) in the initial stage of excitation ($\Delta t = 40$ fs) with a laser fluence of $280 \mu\text{J}/\text{cm}^2$. (e) Intensity difference spectrum obtained by subtracting the equilibrium spectrum in (c) from the excited state signal in (d). The spectra were collected around the Γ -point of the Brillouin zone. The green and black arrows in parts (b) and (c) indicate the surface and bulk bands, respectively. The dashed green lines in (c) indicate the expected dispersion of the topological surface state. (f) Absolute value of normalized intensity difference integrated within the (E, k) -regions demarcated by correspondingly colored boxes in the inset as a function of time delay. (g) Normalized intensity difference integrated within (E, k) -regions demarcated by the colored boxes centered at varying energies placed along the most intense excited band, as shown in the inset. The intensity differences in the insets in parts (f) and (g) are the same as shown in (e).

heterostructure termination.²² This approach has revealed thermal dynamics with a duration of 4 ps in MnBi_2Te_4 across the magnetic ordering temperature²³ as well as photoinduced filling of the surface state hybridization gap of the QL termination in a heterostructure with stoichiometry $m = 3$.²⁴ Here, we determine how carrier extraction and relaxation is controlled by the balance of inter- and intralayer interactions by comparing the time-dependent evolution of excited electronic states between the $m = 0$ and the $m = 1$ heterostructures, i.e., MnBi_2Te_4 and MnBi_4Te_7 . We observe an excited state population in the QL of MnBi_4Te_7 that is generated via an infrared pump pulse. This population is then gradually extracted into the SL with a fluence-dependent delay of up to 350 fs. Thermal relaxation then proceeds at a slower rate within the magnetic SL, implying that the layer-dependent electronic and magnetic properties can be optically controlled on an ultrafast time scale.

Figure 1a presents the SL MnBi_2Te_4 structure, which can be thought of as a QL with an intercalated Mn–Te bilayer, introducing a plane of unpaired spins. Nontrivial topology in this system derives from its Te $5p$ valence band (VB) and Bi $6p$ conduction band (CB) which undergo band inversion due to spin–orbit coupling (SOC).²⁵ The corresponding surface-projected electronic structure obtained from density functional theory (DFT) slab calculations is presented in Figure 1b. The surface and bulk states are indicated by green and black arrows, respectively. In the energy range of our measurement, three branches of bulk bands and two surface bands are observed with the order from lower to higher energy of surface–bulk–bulk–surface–bulk around the Γ -point of the Brillouin zone. The two branches of bulk bands with lower energy exhibit weak out-of-plane-dispersion.^{26,27}

Figure 1c,d presents the electronic dispersion of MnBi_2Te_4 around the Γ -point of the Brillouin zone, measured in

equilibrium conditions before optical excitation ($\Delta t < 0$) and during the initial moments of excitation ($\Delta t = 40$ fs). Figure 1e shows the photoemission intensity difference resulting from subtraction of the equilibrium spectrum from the excited spectrum. The red (blue) regions correspond to gain (loss) of photoemission signal and can be interpreted as excited electron (hole) populations. The spectra display a broad, nearly parabolic distribution of intensity with a minimum at $E - E_F = -0.20$ eV, indicating that the as-grown crystals are significantly electron-doped.²⁸ Note the asymmetric presentation of the $k_{||}$ -scale is due to the fact that we have centered the excited state signal on the detector window, and not the Γ -point, in order to fully capture the dynamics along the band above the Fermi energy E_F . A region of high intensity is concentrated at Γ around $E - E_F = -0.05$ eV, which is consistent with the location of surface states marked by green arrows in Figure 1b. The fainter background intensity, marked by a black arrow in Figure 1c, is primarily composed of bulk conduction band (BCB) states, as seen via a comparison with Figure 1b. During excitation, we observe that the bands crossing E_F become occupied up to $E - E_F = 0.20$ eV with high excited state signal above the central surface states. These features have previously been attributed to a Rashba-like spin splitting,²⁶ suggesting a significant nonequilibrium occupation of spin-polarized carriers in this system. The topological surface state in the bulk band gap (below $E - E_F = -0.20$ eV), reported to be a gapless Dirac cone in previous works,^{29–31} is not resolved due to the low cross-section compared with the CB states at our probe polarization and photon energy.²⁷

The time dependence of electron (hole) dynamics in the BCB and surface states is examined by integrating the intensity within an (E, k) -region spanning 40 meV and $0.03 \text{ \AA}^{-1}$, respectively, centered ± 40 meV above (below) E_F . These integration regions are placed at different k -values for electrons

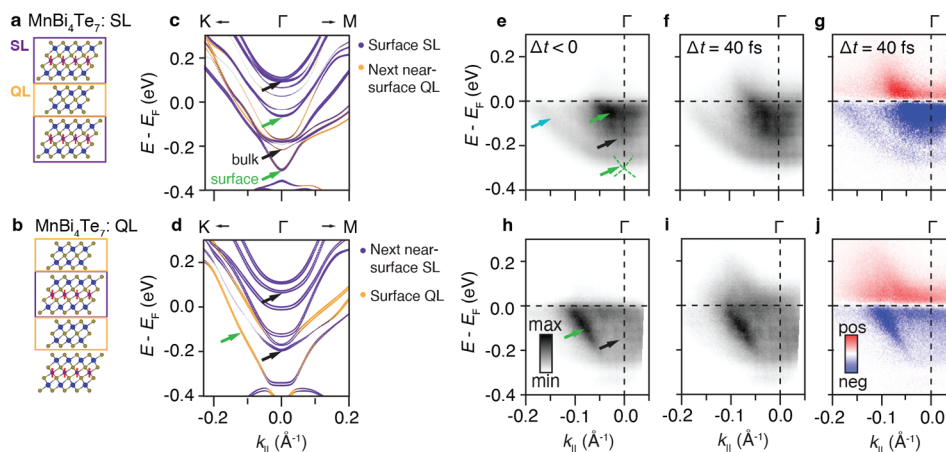


Figure 2. Surface termination dependent electron dynamics in MnBi_4Te_7 . (a, b) Layered crystal structures of MnBi_4Te_7 with a SL or QL exposed at the surface. The red arrows indicate spins on the Mn atoms. (c, d) Dispersions obtained from DFT slab calculations for MnBi_4Te_7 with (c) SL and (d) QL termination. The SL projected bands are colored purple, while the QL projected bands are colored orange. (e–j) TR-ARPES spectra and intensity difference for (e–g) SL termination and (h–j) QL termination. The data are presented similarly as for MnBi_2Te_4 in Figure 1c–e. The measurements were performed with a laser fluence of $280 \mu\text{J}/\text{cm}^2$. Arrows in (c)–(e) and (h) indicate surface (green), bulk (black), and surface-induced Rashba (light blue) bands. Dashed green lines in (e) indicate the expected dispersion of the topological surface state.

and holes in order to track the intensity difference for regions composed mainly of BCB (intensity away from Γ) or surface bands (intensity around Γ). Figure 1f presents the resulting time-dependent intensity around E_F for electrons, represented by red and orange curves, as well as holes, represented by light and dark blue curves that are color-coded according to the integration regions in the inset. The intensity due to excited carriers initially matches the pump–probe cross-correlation integral (see the dashed peak in Figure 1f). The increase in signal then slows down before reaching a plateau, which is followed by a decay back to equilibrium that is achieved around 5 ps after the excitation. The intensity difference corresponding to excited holes at -40 meV reaches its maximum at $\Delta t \approx 0.2$ ps. For excited electrons at 40 meV, the maximum excitation density is achieved significantly later at $\Delta t \approx 0.8$ ps. The E -dependent decay dynamics is determined by inspecting the intensity difference integrated in (E, k) -regions tracking the intense surface band, as shown in Figure 1g. The signal furthest from E_F rapidly increases during excitation and then decays exponentially, while the transient population of excited electrons closer to E_F builds up more slowly. This behavior is consistent with the cascading of intraband scattering processes from higher-lying states.^{32,33} The faster transient buildup of holes close to E_F observed in Figure 1f,g reveals an apparent asymmetry in electron and hole dynamics, which is indicative of a shift of the chemical potential induced by the photodoping.³⁴ Such a shift is demonstrated in Figure S1. The slower decay dynamics of excited electrons and holes close to E_F is driven by the evolution of the electronic temperature and associated Fermi–Dirac distribution after excitation when a quasi-thermal equilibrium is attained.³⁴

We now turn to the MnBi_4Te_7 heterostructure composed of alternating SL and QL units, as sketched in Figure 2a,b. Cleaving the bulk crystal can expose either of these terminations, which exhibit distinct surface electronic structures that we can separately resolve in our TR-ARPES experiment, as shown in Figure S2. Bulk- and surface-derived bands are distinguished via DFT slab calculations of the surface-projected band structures associated with the two terminations, as shown in Figure 2c,d. The calculated

dispersions exhibit a gapped Dirac cone for the SL surface and hybridization bands between the two layers near the QL surface, in agreement with previous studies.¹⁹ TR-ARPES spectra acquired within the same energy range for both terminations are presented in Figure 2e–j. Both terminations exhibit a similar level of electron-doping as MnBi_2Te_4 , causing the photoemission intensity to mainly consist of contributions from BCB and surface states around E_F . Regions of high intensity measured at the SL termination do not coincide with regions of high intensity at the QL termination due to the surface-specific character of these bands (see green arrows in Figure 2e,h). This assignment of band character is supported by the calculations for the SL termination that show bulk bands concentrated in the range of 0.1 – 0.2 eV below E_F around Γ , whereas the bands immediately below E_F are surface states. Regions of high intensity for the QL termination originate from hybridized surface bands. For both SL and QL terminations, the fainter background signals are consistent with BCB states that are identified via black arrows in Figure 2c–e,h. Finally, the SL termination supports a surface-induced Rashba band marked by a light-blue arrow in Figure 2e, which is not reproduced by DFT calculations.^{35,36}

The spectra acquired for $\Delta t = 40$ fs and the intensity difference calculated by subtracting the corresponding spectra measured for $\Delta t < 0$ in Figure 2f,g,i,j reveal significant electron and hole populations in the surface band around Γ at the SL termination, whereas the QL termination exhibits a strong signal due to holes in the surface band and mainly excited electrons in the bulk states above E_F upon photoexcitation. The time-dependence of the intensity difference in selected (E, k) -regions is analyzed for the two terminations in Figure S3, similarly as shown for MnBi_2Te_4 in Figures 1f,g. The asymmetry between excited electron and hole signals driven by a chemical potential shift diminishes from MnBi_2Te_4 to SL-terminated MnBi_4Te_7 and is absent in QL-terminated MnBi_4Te_7 , consistent with significant interlayer charge transfer in MnBi_4Te_7 .

Having established the dispersion and response to photoexcitation across MnBi_2Te_4 and both MnBi_4Te_7 surface terminations, we are now in a position to disentangle the

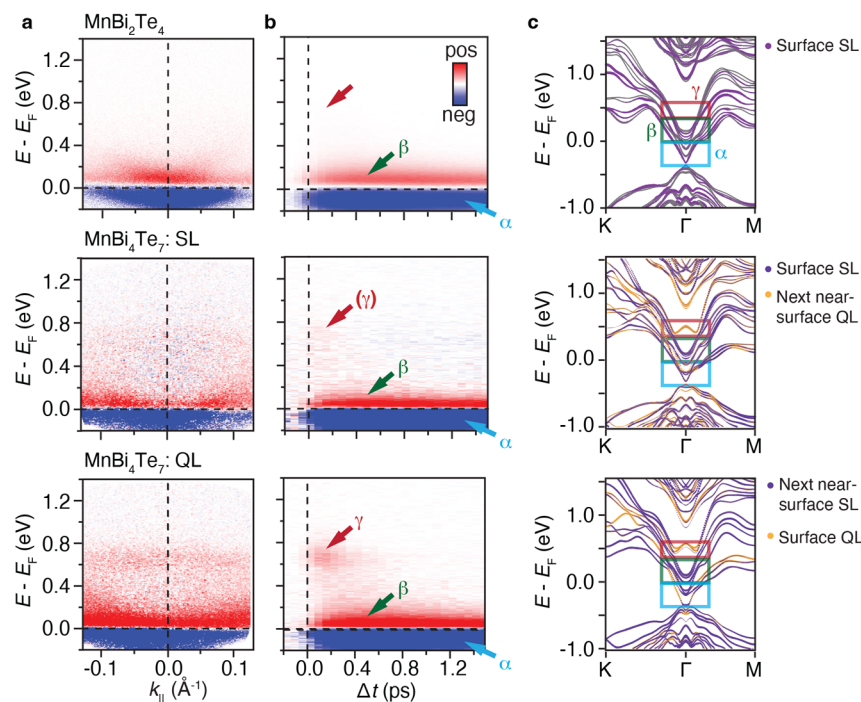


Figure 3. Intra- and interband dynamics in the van der Waals heterostructures MnBi₂Te₄ and MnBi₄Te₇. (a) Intensity difference spectra of MnBi₂Te₄ and SL and QL terminations of MnBi₄Te₇ obtained by subtracting an average of the equilibrium spectrum measured at $\Delta t < 0$ from the excited state signal at $\Delta t = 40$ fs. (b) Energy-distribution curves (EDCs) extracted at Γ as a function of time delay for MnBi₂Te₄ (top), SL (middle), and QL (bottom) terminations of MnBi₄Te₇. The average laser fluence is $300 \mu\text{J}/\text{cm}^2$ for the data sets presented here. (c) DFT-calculated slab bands for the structures indicated in (a) in the same row. The colored boxed areas in (c) and correspondingly colored arrows in (b) indicate regions of distinct dynamics labeled as α , β , and γ .

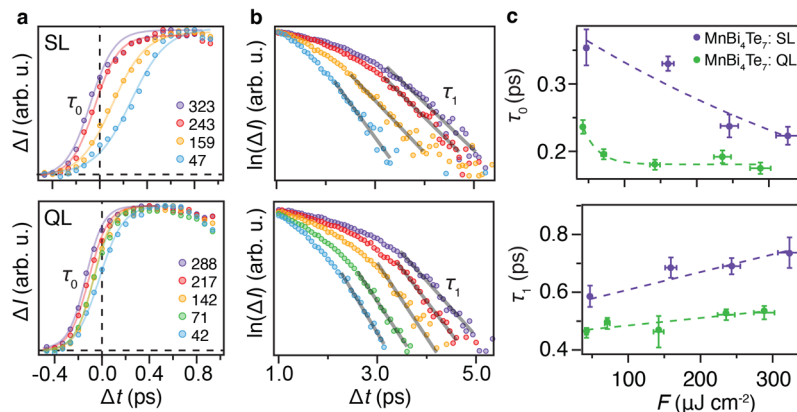


Figure 4. Charge transfer and phonon relaxation in MnBi₄Te₇. (a, b) (E, k) -integrated intensity difference from 0 to 70 meV above E_F and from -0.2 to $0.2 \text{\AA}^{-1}$ for SL and QL terminations of MnBi₄Te₇. Each data set was acquired with the fluence stated in (a) in units of $\mu\text{J}/\text{cm}^2$. In (a) we examine the rising edge of the signal (circles), representing the filling of unoccupied states above E_F , and fit a sigmoid function (curves) to extract the time scale τ_0 of the filling. In (b) we analyze the decay part of the signal on a logarithmic intensity scale and perform exponential fits (lines) to extract the phonon relaxation time scale τ_1 . (c) Extracted time scales from (a) and (b) as a function of laser fluence. Dashed curves provide a guide to the eye.

layer-dependent contributions to the dynamics of the van der Waals-stacked MnBi₂Te₄ and Bi₂Te₃ layers of MnBi₄Te₇. In Figure 3a we inspect the transient occupation of both terminations via the intensity difference at $\Delta t = 40$ fs and compare it with MnBi₂Te₄ in a wider energy window in order to determine where the initially excited electrons are generated. The QL spectrum is characterized by a strong excitation signal 0.7 eV above E_F while only extremely faint intensity is present in this region at the SL termination, likely emerging from the next-nearest QL. These signals are

consistent with spatially resolved pump–probe ARPES spectra obtained on the two terminations using a microfocused beam.²² In analogy with Bi₂Te₃, the shallow excited band may be a surface resonance in the projected bulk band gap.³⁷ Indeed, our slab band structure calculations presented over a wider energy range in Figure 3c indicate that these are QL-derived bands that are absent in the MnBi₂Te₄ system, as seen via the region enclosed by a red box in Figure 3c.

Energy distribution curves (EDCs) extracted at Γ as a function of time delay, displayed in Figure 3b, reveal that the

band at 0.7 eV in the QL is instantaneously occupied followed by a rapid depopulation of excited electrons. Concomitantly, the electron and hole signals grow in the states closer to E_F in both the QL and the SL. The infrared pump pulse initially generates electron–hole pairs via direct transitions from the initially occupied states in both MnBi_2Te_4 and MnBi_4Te_7 .^{32,33} These include the states labeled α in Figure 3, as well as states at lower energy in the VB manifold. In MnBi_2Te_4 , where the QL-derived state at 0.7 eV is absent, excitation proceeds via high-lying bulk states, followed by scattering directly to states close to E_F . See Figures S4 and S5 for further details on the bulk band structures and symmetries of the high-lying states. In MnBi_4Te_7 , we propose that a fraction of excited carriers rapidly occupy the state at 0.7 eV (labeled γ) in the QLs of the van der Waals stack (on a faster time-scale than our experiment can resolve). Carriers are then extracted to the unoccupied states (labeled β) above E_F in both the QL and the SL via interband charge transfer with a time scale given by τ_0 . A cascade of intraband scattering then results in excited carriers trickling down these states and finally recombining with holes via electron–phonon coupling on a time scale labeled as τ_1 .

The optical tunability of inter- and intralayer charge transfer and phonon relaxation between the QL and the SL of MnBi_4Te_7 is demonstrated in Figure 4. We analyze the (E, k) -integrated intensity difference in the initially unoccupied states within 70 meV of E_F as a function of laser fluence and consider separately the rise part of the signal in Figure 4a and the decay part on a logarithmic intensity scale in Figure 4b. The initial increase of the signal in Figure 4a is highly fluence-dependent in the SL, exhibiting a significantly slower time scale with decreasing fluence, whereas the QL rise signal is faster and less sensitive to the fluence. In all cases, the rising part of the signal is well-described by a fit to a sigmoid function given by $(1 + \exp(2.35\Delta t/\tau_0))^{-1}$, providing an estimate of the charge transfer time, τ_0 . After the initial increase in the intensity, the excited state population enters a plateau region. This occurs due to the competition between the charge being transferred from the γ -state in the QL into the β -states in both the SL and the QL and their subsequent recombination with holes. Finally, when the rate of refilling becomes slower than the electron–hole recombination processes, the transient occupation diminishes exponentially, as shown in Figure 4b. We quantify the time scale τ_1 of this process via the slope of a linear fit to the logarithm of the trace in Figure 4b.

The extracted fluence dependences of τ_0 and τ_1 are shown in Figure 4c. The growth rate of the population in the SL reaches a maximum of $\tau_0 = 0.35$ ps at a low fluence of $47 \mu\text{J}/\text{cm}^2$, such that the population reaches its peak at around $\Delta t = 0.80$ ps. This is substantially delayed compared to the peak being reached around $\Delta t = 0.40$ ps for $\tau_0 = 0.22$ ps at a high fluence of $323 \mu\text{J}/\text{cm}^2$. As we are considering the population in an energy range immediately above E_F , the rise time is strongly affected by interlayer charge transfer from the excited carriers in the γ -state in the QL. For low fluence, the intralayer filling of states from γ - to β -bands is more favorable than the interlayer charge transfer to the SL CB. Therefore, the filling rate of β -bands in the SL is slower for low excitation densities. For high excitation density, on the other hand, a large initial population is generated in the QL, thereby removing this bottleneck effect. For the QL termination, τ_0 exhibits a less dramatic fluence dependence and merely reflects the efficiency of intralayer interband scattering.

Finally, the decay time τ_1 provides information on electron–hole recombination. By comparison to the related systems Bi_2Se_3 ³³ and $\text{Bi}_2\text{Se}_x\text{Te}_{1-x}$ we infer that the relaxation is mediated by energy transfer to phonons. In particular, terahertz spectroscopy studies^{38,39} show a similar fluence-dependent behavior of τ_1 . The decay constant increases with applied fluence, indicating that the electron–phonon coupling becomes less efficient with a larger population of excited carriers. This trend can be explained by the increased screening of the electron–phonon interaction by the photoinduced charge carriers.⁴⁰ The relaxation dynamics extracted in Figure 4c are notably faster for QL than for SL, suggesting that intralayer phonons play a dominant role in the scattering processes. Such behavior is in line with a substantially weakened c -axis interlayer vibrational interaction in the heterostructure⁴¹ in comparison to its nonmagnetic counterpart Bi_2Te_3 .⁴² We note, however, that we cannot distinguish between the involvement of in-plane and out-of-plane intralayer vibrational modes in the scattering process.

In conclusion, we have determined the ultrafast charge carrier dynamics of the intrinsic magnetic topological insulator van der Waals heterostructures MnBi_2Te_4 and MnBi_4Te_7 . The out-of-equilibrium distribution of excited carriers exhibits distinct dynamics that is strongly affected by interlayer interactions between the Bi_2Te_3 quintuple layers and the MnBi_2Te_4 septuple layers. Infrared optical pumping leads to a transient population of carriers in the Bi_2Te_3 layers. These excited carriers are then extracted via interband and interlayer scattering into conduction band states around the Fermi energy within Bi_2Te_3 and in the adjacent MnBi_2Te_4 layers, respectively. In the regime of low laser fluence, the charge transfer processes into the MnBi_2Te_4 layers exhibit a bottleneck, potentially enabling optical control of the population of spin-polarized carriers in the magnetic layers of the van der Waals stack. Furthermore, as the subsequent electron–phonon-mediated relaxation is less efficient in the magnetic MnBi_2Te_4 compared to the nonmagnetic Bi_2Te_3 layers, it might be feasible to optically modify the magnetic properties of the heterostructure when designing spintronic and optoelectronic devices with layers of MnBi_2Te_4 .

METHODS

Sample Growth. The MnBi_2Te_4 and MnBi_4Te_7 crystals were grown by the flux method. High purity Mn, Bi, and Te powders were sealed in quartz tubes with a Mn:Bi:Te ratio of 1:10:16. The tubes were heated to 900 °C and then cooled to 595/590 °C, respectively. The flux was removed by centrifugation after cooling.

Photoemission Experiments. The TR-ARPES measurements were performed at the T-ReX facility (Trieste, Italy). Pump and probe pulses were generated by a 250 kHz Ti:sapphire Coherent Reg A laser system, whose output was centered at an energy of 1.55 eV. The fourth harmonic (6.2 eV) of the fundamental beam was used as an s -polarized probe pulse. The remainder of the beam was used as a p -polarized pump with a tunable fluence in the range of 40–280 $\mu\text{J}/\text{cm}^2$, arriving at the sample at a variable time delay, Δt , with respect to the probe. The experimental time, energy, and angular resolution were better than 200 fs, 50 meV and 0.2°, respectively. The samples were cleaved *in situ* at a base pressure of 2×10^{-10} mbar at room temperature and kept at a temperature of 100–110 K during the measurement.

Density Functional Theory Calculations. Band structures of MnBi_2Te_4 and MnBi_4Te_7 were calculated by DFT,^{43,44} which was carried out by the Vienna ab initio simulation package (VASP)⁴⁵ based on the projector augmented wave (PAW) method.⁴⁶ The exchange–correlation functional was described by the generalized gradient approximation with the Perdew–Burke–Ernzerhof formalism (PBE)⁴⁷ with the on-site Coulomb interaction Hubbard $U = 5$ eV for electrons on d-orbitals of Mn atoms. The total energy convergence criteria were set to 1.0×10^{-6} eV including spin–orbit coupling (SOC). The plane-wave cutoff energy was set to 400 eV. We employed an $11 \times 11 \times 1$ Monkhorst–Pack grid to sample the whole Brillouin zone for both of the slab structures. Our slab band structures of MnBi_2Te_4 were obtained from slab calculations with the thickness of 6 van der Waals layers, while those of QL and SL terminations of MnBi_4Te_7 employed 5 and 7 van der Waals layers, respectively. The magnetic configurations were A-type AFM for both cases with 4.6 μB magnetic moments on the Mn atoms.

■ ASSOCIATED CONTENT

SI Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acs.nanolett.2c03075>.

Five sections containing five figures describing the chemical potential shift induced by the pump pulse, the method to resolve the two terminations of MnBi_4Te_7 in the TR-ARPES experiment, the E - and k -dependent dynamics of MnBi_4Te_7 , bulk band structure calculations of MnBi_2Te_4 and MnBi_4Te_7 , and the symmetry of unoccupied states (PDF)

■ AUTHOR INFORMATION

Corresponding Author

Søren Ulstrup – Department of Physics and Astronomy, Interdisciplinary Nanoscience Center, Aarhus University, 8000 Aarhus C, Denmark; orcid.org/0000-0001-5922-4488; Email: ulstrup@phys.au.dk

Authors

Paulina Ewa Majchrzak – Department of Physics and Astronomy, Interdisciplinary Nanoscience Center, Aarhus University, 8000 Aarhus C, Denmark; orcid.org/0000-0002-5200-3866

Yuntian Liu – Department of Physics and Shenzhen Institute for Quantum Science and Engineering (SIQSE), Southern University of Science and Technology, Shenzhen 518055, China

Klara Volckaert – Department of Physics and Astronomy, Interdisciplinary Nanoscience Center, Aarhus University, 8000 Aarhus C, Denmark

Deepnarayan Biswas – Department of Physics and Astronomy, Interdisciplinary Nanoscience Center, Aarhus University, 8000 Aarhus C, Denmark

Chakradhar Sahoo – Department of Physics and Astronomy, Interdisciplinary Nanoscience Center, Aarhus University, 8000 Aarhus C, Denmark

Denny Puntel – Dipartimento di Fisica, Università degli Studi di Trieste, 34127 Trieste, Italy

Wibke Bronsch – Elettra - Sincrotrone Trieste S.C.p.A., 34149 Basovizza, Italy; orcid.org/0000-0002-6012-9290

Manuel Tuniz – Dipartimento di Fisica, Università degli Studi di Trieste, 34127 Trieste, Italy

Federico Cilento – Elettra - Sincrotrone Trieste S.C.p.A., 34149 Basovizza, Italy

Xing-Chen Pan – Advanced Institute for Materials Research, Tohoku University, Sendai 980-8577, Japan

Qihang Liu – Department of Physics and Shenzhen Institute for Quantum Science and Engineering (SIQSE), Southern University of Science and Technology, Shenzhen 518055, China

Yong P. Chen – Department of Physics and Astronomy, Interdisciplinary Nanoscience Center, Aarhus University, 8000 Aarhus C, Denmark; Advanced Institute for Materials Research, Tohoku University, Sendai 980-8577, Japan; Department of Physics and Astronomy, School of Electrical and Computer Engineering, and Purdue Quantum Science and Engineering Institute, Purdue University, West Lafayette, Indiana 47907, United States

Complete contact information is available at:

<https://pubs.acs.org/doi/10.1021/acs.nanolett.2c03075>

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

We gratefully acknowledge funding from VILLUM FONDEN through the Young Investigator Program (Grant. No. 15375), the Villum Investigator Program (Grant. No. 25931), the Centre of Excellence for Dirac Materials (Grant. No. 11744), and the Danish Council for Independent Research, Natural Sciences, under the Sapere Aude program (Grant No. DFF-9064-00057B). Work at the Advanced Institute for Materials Research has benefited from the support of WPI-AIMR, JSPS KAKENHI Basic Science A (18H03858), New Science (18H04473 and 20H04623), and Tohoku University FRIID program. C.S. acknowledges the Marie Skłodowska-Curie Postdoctoral Fellowship (Proposal Number 101059528). Work at SUSTech was supported by National Key R&D Program of China under Grant No. 2020YFA0308900 and the Center for Computational Science and Engineering of Southern University of Science and Technology.

■ REFERENCES

- (1) Jin, C.; Ma, E. Y.; Karni, O.; Regan, E. C.; Wang, F.; Heinz, T. F. Ultrafast dynamics in van der Waals heterostructures. *Nat. Nanotechnol.* **2018**, *13*, 994–1003.
- (2) Hong, X.; Kim, J.; Shi, S.-F.; Zhang, Y.; Jin, C.; Sun, Y.; Tongay, S.; Wu, J.; Zhang, Y.; Wang, F. Ultrafast charge transfer in atomically thin MoS_2/WS_2 heterostructures. *Nat. Nanotechnol.* **2014**, *9*, 682–686.
- (3) Zheng, Q.; Saidi, W. A.; Xie, Y.; Lan, Z.; Prezhd, O. V.; Petek, H.; Zhao, J. Phonon-Assisted Ultrafast Charge Transfer at van der Waals Heterostructure Interface. *Nano Lett.* **2017**, *17*, 6435–6442.
- (4) Gong, Y.; Guo, J.; Li, J.; Zhu, K.; Liao, M.; Liu, X.; Zhang, Q.; Gu, L.; Tang, L.; Feng, X.; et al. Experimental realization of an intrinsic magnetic topological insulator. *Chin. Phys. Lett.* **2019**, *36*, 076801.
- (5) Otrokov, M.; Rusinov, I. P.; Blanco-Rey, M.; Hoffmann, M.; Vyazovskaya, A. Y.; Eremin, S.; Ernst, A.; Echenique, P. M.; Arnau, A.; Chulkov, E. V. Unique thickness-dependent properties of the van der Waals interlayer antiferromagnet MnBi_2Te_4 films. *Physical review letters* **2019**, *122*, 107202.
- (6) Zhang, D.; Shi, M.; Zhu, T.; Xing, D.; Zhang, H.; Wang, J. Topological axion states in the magnetic insulator MnBi_2Te_4 with

the quantized magnetoelectric effect. *Physical review letters* **2019**, *122*, 206401.

(7) Li, J.; Li, Y.; Du, S.; Wang, Z.; Gu, B.-L.; Zhang, S.-C.; He, K.; Duan, W.; Xu, Y. Intrinsic magnetic topological insulators in van der Waals layered MnBi₂Te₄-family materials. *Science Advances* **2019**, *5*, No. eaaw5685.

(8) Otrokov, M. M.; Klimovskikh, I. I.; Bentmann, H.; Estyunin, D.; Zeugner, A.; Aliev, Z. S.; Gaß, S.; Wolter, A.; Koroleva, A.; Shikin, A. M.; et al. Prediction and observation of an antiferromagnetic topological insulator. *Nature* **2019**, *576*, 416–422.

(9) Deng, Y.; Yu, Y.; Shi, M. Z.; Guo, Z.; Xu, Z.; Wang, J.; Chen, X. H.; Zhang, Y. Quantum anomalous Hall effect in intrinsic magnetic topological insulator MnBi₂Te₄. *Science* **2020**, *367*, 895–900.

(10) Liu, C.; Wang, Y.; Li, H.; Wu, Y.; Li, Y.; Li, J.; He, K.; Xu, Y.; Zhang, J.; Wang, Y. Robust axion insulator and Chern insulator phases in a two-dimensional antiferromagnetic topological insulator. *Nat. Mater.* **2020**, *19*, 522–527.

(11) Zhao, Y.; Liu, Q. Routes to realize the axion-insulator phase in MnBi₂Te₄ (Bi₂Te₃)_n family. *Appl. Phys. Lett.* **2021**, *119*, 060502.

(12) Gu, M.; Li, J.; Sun, H.; Zhao, Y.; Liu, C.; Liu, J.; Lu, H.; Liu, Q. Spectral signatures of the surface anomalous Hall effect in magnetic axion insulators. *Nat. Commun.* **2021**, *12*, 3524.

(13) Deng, H.; Chen, Z.; Wołos, A.; Konczykowski, M.; Sobczak, K.; Sitnicka, J.; Fedorchenko, I. V.; Borysiuk, J.; Heider, T.; Pluciński, Ł.; Park, K.; Georgescu, A. B.; Cano, J.; Krusin-Elbaum, L. High-temperature quantum anomalous Hall regime in a MnBi₂Te₄/Bi₂Te₃ superlattice. *Nat. Phys.* **2021**, *17*, 36–42.

(14) Otrokov, M. M.; Menshchikova, T. V.; Vergniory, M. G.; Rusinov, I. P.; Yu Vyazovskaya, A.; Koroteev, Y. M.; Bihlmayer, G.; Ernst, A.; Echenique, P. M.; Arnau, A.; Chulkov, E. V. Highly-ordered wide bandgap materials for quantized anomalous Hall and magnetoelectric effects. *2D Materials* **2017**, *4*, 025082.

(15) Sun, H.; Xia, B.; Chen, Z.; Zhang, Y.; Liu, P.; Yao, Q.; Tang, H.; Zhao, Y.; Xu, H.; Liu, Q. Rational design principles of the quantum anomalous Hall effect in superlattice-like magnetic topological insulators. *Physical review letters* **2019**, *123*, 096401.

(16) Wu, J.; Liu, F.; Sasase, M.; Ienaga, K.; Obata, Y.; Yukawa, R.; Horiba, K.; Kumigashira, H.; Okuma, S.; Inoshita, T.; et al. Natural van der Waals heterostructural single crystals with both magnetic and topological properties. *Science advances* **2019**, *5*, No. eaax9989.

(17) Xu, L.; et al. Persistent surface states with diminishing gap in MnBi₂Te₄/Bi₂Te₃ superlattice antiferromagnetic topological insulator. *Science Bulletin* **2020**, *65*, 2086–2093.

(18) Hu, Y.; Xu, L.; Shi, M.; Luo, A.; Peng, S.; Wang, Z. Y.; Ying, J. J.; Wu, T.; Liu, Z. K.; Zhang, C. F.; Chen, Y. L.; Xu, G.; Chen, X.-H.; He, J.-F. Universal gapless Dirac cone and tunable topological states in (MnBi₂Te₄)_m(Bi₂Te₃)_n heterostructures. *Phys. Rev. B* **2020**, *101*, 161113.

(19) Wu, X.; Li, J.; Ma, X.-M.; Zhang, Y.; Liu, Y.; Zhou, C.-S.; Shao, J.; Wang, Q.; Hao, Y.-J.; Feng, Y.; et al. Distinct topological surface states on the two terminations of MnBi₄Te₇. *Physical Review X* **2020**, *10*, 031013.

(20) Hu, C.; Gordon, K. N.; Liu, P.; Liu, J.; Zhou, X.; Hao, P.; Narayan, D.; Emmanouilidou, E.; Sun, H.; Liu, Y.; et al. A van der Waals antiferromagnetic topological insulator with weak interlayer magnetic coupling. *Nat. Commun.* **2020**, *11*, 97.

(21) Lu, R.; Sun, H.; Kumar, S.; Wang, Y.; Gu, M.; Zeng, M.; Hao, Y.-J.; Li, J.; Shao, J.; Ma, X.-M.; et al. Half-magnetic topological insulator with magnetization-induced Dirac gap at a selected surface. *Physical Review X* **2021**, *11*, 011039.

(22) Yan, C.; Green, E.; Fukumori, R.; Protic, N.; Lee, S. H.; Fernandez-Mulligan, S.; Raja, R.; Erdakos, R.; Mao, Z.; Yang, S. An integrated quantum material testbed with multi-resolution photoemission spectroscopy. *Rev. Sci. Instrum.* **2021**, *92*, 113907.

(23) Nevala, D.; Li, H. X.; Yan, J.-Q.; Moore, R. G.; Lee, H.-N.; Miao, H.; Johnson, P. D. Coexistence of Surface Ferromagnetism and a Gapless Topological State in MnBi₂Te₄. *Phys. Rev. Lett.* **2020**, *125*, 117205.

(24) Zhong, H.; Bao, C.; Wang, H.; Li, J.; Yin, Z.; Xu, Y.; Duan, W.; Xia, T.-L.; Zhou, S. Light-Tunable Surface State and Hybridization Gap in Magnetic Topological Insulator MnBi₈Te₁₃. *Nano Lett.* **2021**, *21*, 6080–6086.

(25) Li, H.; et al. Dirac Surface States in Intrinsic Magnetic Topological Insulators EuSn₂As₂ and MnBi_{2n}Te_{3n+1}. *Phys. Rev. X* **2019**, *9*, 041039.

(26) Estyunin, D. A.; Klimovskikh, I. I.; Shikin, A. M.; Schwier, E. F.; Otrokov, M. M.; Kimura, A.; Kumar, S.; Filnov, S. O.; Aliev, Z. S.; Babanly, M. B.; Chulkov, E. V. Signatures of temperature driven antiferromagnetic transition in the electronic structure of topological insulator MnBi₂Te₄. *APL Materials* **2020**, *8*, 021105.

(27) Yan, C.; Fernandez-Mulligan, S.; Mei, R.; Lee, S. H.; Protic, N.; Fukumori, R.; Yan, B.; Liu, C.; Mao, Z.; Yang, S. Origins of electronic bands in the antiferromagnetic topological insulator MnBi₂Te₄. *Phys. Rev. B* **2021**, *104*, L041102.

(28) Zeugner, A.; Nietschke, F.; Wolter, A. U. B.; Gaß, S.; Vidal, R. C.; Peixoto, T. R. F.; Pohl, D.; Damm, C.; Lubk, A.; Hentrich, R.; et al. Chemical Aspects of the Candidate Antiferromagnetic Topological Insulator MnBi₂Te₄. *Chem. Mater.* **2019**, *31*, 2795–2806.

(29) Hao, Y.-J.; et al. Gapless Surface Dirac Cone in Antiferromagnetic Topological Insulator MnBi₂Te₄. *Phys. Rev. X* **2019**, *9*, 041038.

(30) Li, H.; et al. Dirac Surface States in Intrinsic Magnetic Topological Insulators EuSn₂As₂ and MnBi_{2n}Te_{3n+1}. *Phys. Rev. X* **2019**, *9*, 041039.

(31) Chen, Y. J.; et al. Topological Electronic Structure and Its Temperature Evolution in Antiferromagnetic Topological Insulator MnBi₂Te₄. *Phys. Rev. X* **2019**, *9*, 041040.

(32) Hajlaoui, M.; Papalazarou, E.; Mauchain, J.; Lantz, G.; Moisan, N.; Boschetto, D.; Jiang, Z.; Miotkowski, I.; Chen, Y. P.; Taleb-Ibrahimi, A.; Perfetti, L.; Marsi, M. Ultrafast Surface Carrier Dynamics in the Topological Insulator Bi₂Te₃. *Nano Lett.* **2012**, *12*, 3532–3536.

(33) Sobota, J. A.; Yang, S.; Analytis, J. G.; Chen, Y. L.; Fisher, I. R.; Kirchmann, P. S.; Shen, Z.-X. Ultrafast Optical Excitation of a Persistent Surface-State Population in the Topological Insulator Bi₂Se₃. *Phys. Rev. Lett.* **2012**, *108*, 117403.

(34) Crepaldi, A.; Ressel, B.; Cilento, F.; Zacchigna, M.; Grazioli, C.; Berger, H.; Bugnon, P.; Kern, K.; Grioni, M.; Parmigiani, F. Ultrafast photodoping and effective Fermi–Dirac distribution of the Dirac particles in Bi₂Se₃. *Phys. Rev. B* **2012**, *86*, 205133.

(35) Wu, X.; et al. Distinct Topological Surface States on the Two Terminations of MnBi₄Te₇. *Phys. Rev. X* **2020**, *10*, 031013.

(36) Vidal, R. C.; et al. Orbital Complexity in Intrinsic Magnetic Topological Insulators MnBi₄Te₇ and MnBi₆Te₁₀. *Phys. Rev. Lett.* **2021**, *126*, 176403.

(37) Sánchez-Barriga, J.; Battiato, M.; Krivenkov, M.; Golias, E.; Varykhalov, A.; Romualdi, A.; Yashina, L. V.; Minár, J.; Kornilov, O.; Ebert, H.; Held, K.; Braun, J. Subpicosecond spin dynamics of excited states in the topological insulator Bi₂Te₃. *Phys. Rev. B* **2017**, *95*, 125405.

(38) Li, G.; Zhou, W.; Zhang, W.; Ma, G.; Cui, H.; Gao, Y.; Huang, Z.; Chu, J. Pump fluence dependence of ultrafast carrier dynamics in InSb measured by optical pump-terahertz probe spectroscopy. *Appl. Opt.* **2018**, *57*, 9729–9734.

(39) Reinhofer, C.; Mukai, Y.; Germanskiy, S.; Bliesener, A.; Lippertz, G.; Uday, A.; Taskin, A. A.; Ando, Y.; Wang, Z.; van Loosdrecht, P. H. M. Relaxation dynamics of the optically driven nonequilibrium states in the electron- and hole-doped topological-insulator materials (Bi_{1-x}Sb_x)₂Te₃. *Phys. Rev. Materials* **2020**, *4*, 124201.

(40) Heid, R.; Sklyadneva, I. Y.; Chulkov, E. V. Electron-phonon coupling in topological surface states: The role of polar optical modes. *Sci. Rep.* **2017**, *7*, 1095.

(41) Cho, Y.; Kang, J. H.; Liang, L.; Taylor, M.; Kong, X.; Ghosh, S.; Kargar, F.; Hu, C.; Balandin, A. A.; Poretzky, A. A.; Ni, N.; Wong, C. W. Phonon modes and Raman signatures of MnBi_{2n}Te_{3n+1} (*n* = 1, 2, 3,

4) magnetic topological heterostructures. *Phys. Rev. Research* **2022**, *4*, 013108.

(42) Liang, L.; Zhang, J.; Sumpter, B. G.; Tan, Q.-H.; Tan, P.-H.; Meunier, V. Low-Frequency Shear and Layer-Breathing Modes in Raman Scattering of Two-Dimensional Materials. *ACS Nano* **2017**, *11*, 11777–11802.

(43) Hohenberg, P.; Kohn, W. Inhomogeneous Electron Gas. *Phys. Rev.* **1964**, *136*, B864–B871.

(44) Kohn, W.; Sham, L. J. Self-Consistent Equations Including Exchange and Correlation Effects. *Phys. Rev.* **1965**, *140*, A1133–A1138.

(45) Kresse, G.; Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **1996**, *54*, 11169–11186.

(46) Kresse, G.; Joubert, D. From ultrasoft pseudopotentials to the projector augmented-wave method. *Phys. Rev. B* **1999**, *59*, 1758–1775.

(47) Perdew, J. P.; Burke, K.; Ernzerhof, M. Generalized Gradient Approximation Made Simple. *Phys. Rev. Lett.* **1996**, *77*, 3865–3868.

Recommended by ACS

Selectively Controlled Ferromagnets by Electric Fields in van der Waals Ferromagnetic Heterojunctions

Zi-Ao Wang, Kaiyou Wang, *et al.*

JANUARY 10, 2023
NANO LETTERS

READ 

Interlayer Exciton–Phonon Bound State in Bi₂Se₃/Monolayer WS₂ van der Waals Heterostructures

Zachariah Hennighausen, Berend T. Jonker, *et al.*

JANUARY 16, 2023
ACS NANO

READ 

Enhancement of Perpendicular Magnetic Anisotropy and Curie Temperature in V-Doped Two-Dimensional CrSI Janus Semiconductor Monolayer

Ruilin Han, Yu Yan, *et al.*

JANUARY 19, 2023
THE JOURNAL OF PHYSICAL CHEMISTRY C

READ 

Ultrastrong Optical Harmonic Generations in Layered Platinum Disulfide in the Mid-Infrared

Song Zhu, Qi Jie Wang, *et al.*

JANUARY 27, 2023
ACS NANO

READ 

Get More Suggestions >